



Aalborg Universitet

AALBORG UNIVERSITY
DENMARK

Structural Evolution in a Melt-Quenched Zeolitic Imidazolate Framework Glass during Heat-treatment

Zhang, Jiayan; Longley, L.; Liu, Hao; Ashling, C.W.; Chater, P.A.; Beyer, K.A.; Chapman, K.W.; Tao, H.Z.; Keen, D.A.; Bennett, T.D.; Yue, Yuanzheng

Published in:
Chemical Communications

DOI (link to publication from Publisher):
[10.1039/c8cc09574d](https://doi.org/10.1039/c8cc09574d)

Publication date:
2019

Document Version
Accepted author manuscript, peer reviewed version

[Link to publication from Aalborg University](#)

Citation for published version (APA):
Zhang, J., Longley, L., Liu, H., Ashling, C. W., Chater, P. A., Beyer, K. A., Chapman, K. W., Tao, H. Z., Keen, D. A., Bennett, T. D., & Yue, Y. (2019). Structural Evolution in a Melt-Quenched Zeolitic Imidazolate Framework Glass during Heat-treatment. *Chemical Communications*, 55(17), 2521-2524. [17].
<https://doi.org/10.1039/c8cc09574d>

General rights


Copyright and moral rights for the publications made accessible in the public portal are retained by the authors and/or other copyright owners and it is a condition of accessing publications that users recognise and abide by the legal requirements associated with these rights.

- Users may download and print one copy of any publication from the public portal for the purpose of private study or research.
- You may not further distribute the material or use it for any profit-making activity or commercial gain
- You may freely distribute the URL identifying the publication in the public portal -

Take down policy

If you believe that this document breaches copyright please contact us at vbn@aub.aau.dk providing details, and we will remove access to the work immediately and investigate your claim.

We have presented the Graphical Abstract text and image for your article below. This brief summary of your work will appear in the contents pages of the issue in which your article appears.

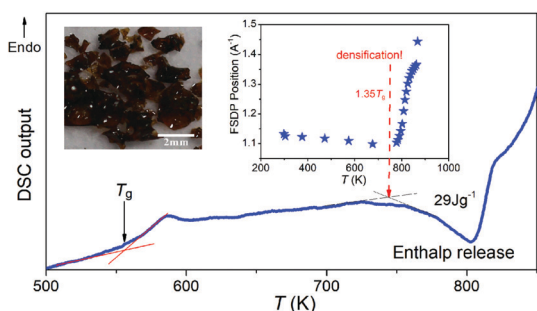

Structural evolution in a melt-quenched zeolitic imidazolate framework glass during heat-treatment

Jiayan Zhang, Louis Longley, Hao Liu, Christopher W. Ashling, Philip A. Chater, Kevin A. Beyer, Karena W. Chapman, Haizheng Tao, David A. Keen, Thomas D. Bennett* and Yuanzheng Yue*

A pronounced enthalpy release occurs around $1.38T_g$ in the prototypical metal–organic framework glass formed from ZIF-4 $[\text{Zn}(\text{C}_3\text{H}_3\text{N}_2)_2]$, but there is no sign for any crystallization (*i.e.*, long-range ordering) taking place.

Please check this proof carefully. Our staff will not read it in detail after you have returned it.

Please send your corrections either as a copy of the proof PDF with electronic notes attached or as a list of corrections. **Do not edit the text within the PDF or send a revised manuscript** as we will not be able to apply your corrections. Corrections at this stage should be minor and not involve extensive changes.

Proof corrections must be returned as a single set of corrections, approved by all co-authors. No further corrections can be made after you have submitted your proof corrections as we will publish your article online as soon as possible after they are received.

Please ensure that:

- The spelling and format of all author names and affiliations are checked carefully. You can check how we have identified the authors' first and last names in the researcher information table on the next page. **Names will be indexed and cited as shown on the proof, so these must be correct.**
- Any funding bodies have been acknowledged appropriately and included both in the paper and in the funder information table on the next page.
- All of the editor's queries are answered.
- Any necessary attachments, such as updated images or ESI files, are provided.

Translation errors can occur during conversion to typesetting systems so you need to read the whole proof. In particular please check tables, equations, numerical data, figures and graphics, and references carefully.

Please return your **final** corrections, where possible within **48 hours** of receipt, by e-mail to: chemcomm@rsc.org. If you require more time, please notify us by email.

Funding information

Providing accurate funding information will enable us to help you comply with your funders' reporting mandates. Clear acknowledgement of funder support is an important consideration in funding evaluation and can increase your chances of securing funding in the future.

We work closely with Crossref to make your research discoverable through the Funding Data search tool (<http://search.crossref.org/funding>). Funding Data provides a reliable way to track the impact of the work that funders support. Accurate funder information will also help us (i) identify articles that are mandated to be deposited in **PubMed Central (PMC)** and deposit these on your behalf, and (ii) identify articles funded as part of the **CHORUS** initiative and display the Accepted Manuscript on our web site after an embargo period of 12 months.

Further information can be found on our webpage (<http://rsc.li/funding-info>).

What we do with funding information

We have combined the information you gave us on submission with the information in your acknowledgements. This will help ensure the funding information is as complete as possible and matches funders listed in the Crossref Funder Registry.

If a funding organisation you included in your acknowledgements or on submission of your article is not currently listed in the registry it will not appear in the table on this page. We can only deposit data if funders are already listed in the Crossref Funder Registry, but we will pass all funding information on to Crossref so that additional funders can be included in future.

Please check your funding information

The table below contains the information we will share with Crossref so that your article can be found *via* the Funding Data search tool. **Please check that the funder names and grant numbers in the table are correct and indicate if any changes are necessary to the Acknowledgements text.**

Funder name	Funder's main country of origin	Funder ID (for RSC use only)	Award/grant number
National Natural Science Foundation of China	China	501100001809	51772223
Corning Incorporated Foundation	United States	100008280	Unassigned
Royal Society	United Kingdom	501100000288	RG160498, UF150021
Engineering and Physical Sciences Research Council	United Kingdom	501100000266	Unassigned

Q1

Researcher information

Please check that the researcher information in the table below is correct, including the spelling and formatting of all author names, and that the authors' first, middle and last names have been correctly identified. **Names will be indexed and cited as shown on the proof, so these must be correct.**

If any authors have ORCID or ResearcherID details that are not listed below, please provide these with your proof corrections. Please ensure that the ORCID and ResearcherID details listed below have been assigned to the correct author. Authors should have their own unique ORCID iD and should not use another researcher's, as errors will delay publication.

Please also update your account on our online [manuscript submission system](#) to add your ORCID details, which will then be automatically included in all future submissions. See [here](#) for step-by-step instructions and more information on author identifiers.

First (given) and middle name(s)	Last (family) name(s)	ResearcherID	ORCID iD
Jiayan	Zhang		
Louis	Longley		
Hao	Liu		
Christopher W.	Ashling		
Philip A.	Chater		
Kevin A.	Beyer		
Karena W.	Chapman		
Haizheng	Tao	C-9243-2014	

David A.	Keen		0000-0003-0376-2767
Thomas D.	Bennett		0000-0003-3717-3119
Yuanzheng	Yue		0000-0002-6048-5236

Queries for the attention of the authors

Journal: **ChemComm**

Paper: **c8cc09574d**

Title: **Structural evolution in a melt-quenched zeolitic imidazolate framework glass during heat-treatment**

For your information: You can cite this article before you receive notification of the page numbers by using the following format: (authors), Chem. Commun., (year), DOI: 10.1039/c8cc09574d.

Editor's queries are marked on your proof like this **Q1**, **Q2**, etc. and for your convenience line numbers are indicated like this 5, 10, 15, ...

Please ensure that all queries are answered when returning your proof corrections so that publication of your article is not delayed.

Query reference	Query	Remarks
Q1	Funder details have been incorporated in the funder table using information provided in the article text. Please check that the funder information in the table is correct.	
Q2	Please confirm that the spelling and format of all author names is correct. Names will be indexed and cited as shown on the proof, so these must be correct. No late corrections can be made.	
Q3	Do you wish to add an e-mail address for the corresponding author? If so, please provide the relevant information.	
Q4	Please check that the inserted Graphical Abstract text is suitable. Please ensure that the text fits between the two horizontal lines.	

Structural evolution in a melt-quenched zeolitic imidazolate framework glass during heat-treatment†

Cite this: DOI: 10.1039/c8cc09574d

Received 3rd December 2018,
Accepted 4th February 2019

DOI: 10.1039/c8cc09574d

rsc.li/chemcomm

A pronounced enthalpy release occurs around $1.38T_g$ in the prototypical metal–organic framework glass formed from ZIF-4 [$\text{Zn}(\text{C}_3\text{H}_3\text{N}_2)_2$], but there is no sign for any crystallization (*i.e.*, long-range ordering) taking place. The enthalpy release peak is attributed to pore collapse and structural densification.

Metal–organic frameworks (MOFs) consist of metal clusters or ions linked by organic ligands into large open-networks with various pore architectures.^{1,2} Amongst these, the zeolitic imidazolate frameworks (ZIFs) are of interest due to their excellent chemical stabilities.³ The M–Im–M (M – transition metal, Im – imidazolate, $\text{C}_3\text{H}_3\text{N}_2^-$) angle in ZIFs is analogous to the Si–O–Si bond angle in zeolites, and so many ZIFs adopt zeolitic tetrahedral network topologies.^{4,5} Thermal⁶ and pressure-induced⁷ amorphization of the crystalline state is observed, with one structure, ZIF-4, melting to form a ‘liquid-MOF’ at *ca.* 860 K.⁸ Quenching this liquid yields a glass with a continuous random network of corner-sharing $\text{Zn}(\text{Im})_4$ tetrahedra.⁹ Given the structural similarities to conventional SiO_2 glass, this presents opportunities to study MOF-glasses in the context of existing inorganic glass materials.^{10–12}

In particular, the dynamic properties of the glasses upon heating should be investigated, given the rich behavior of the structural evolution upon heating of other supercooled liquid families.^{13–15} Motivated by an initial study on the glass formed

by melt-quenching ZIF-62 [$\text{Zn}(\text{Im})_{1.75}(\text{bIm})_{0.25}$] (bIm – benzimidazole $\text{C}_7\text{H}_5\text{N}_2^-$), which demonstrates ultrahigh stability against crystallization,¹⁶ here we investigate the effect of heat-treatment upon a melt-quenched zeolitic imidazolate framework glass, formed from ZIF-4 [$\text{Zn}(\text{Im})_2$]. Consistent with prior literature, the ZIF-liquid quenched back to room temperature at a rate of 10 K min^{-1} is referred to as $a_g\text{ZIF-4}$.¹⁷

Differential scanning calorimetry (DSC) experiments were performed on a crystalline sample of ZIF-4, and show desolvation, amorphization, recrystallization (to the dense ZIF-zni phase, also of composition $\text{Zn}(\text{Im})_2$), and subsequent melting events. These are labelled features A–D respectively, in the black dashed curve in Fig. 1, and are consistent with previous results.⁹ In a second experiment, a sample of ZIF-4 was heated to 853 K, *i.e.*, above the melting temperature, T_m , and quenched back to room temperature at a rate of 20 K min^{-1} , which is twice as fast as the quench rate used for previous ZIF-4 glass samples. The resultant material is termed $fq\text{-}a_g\text{ZIF-4}$ (*fq* – fast

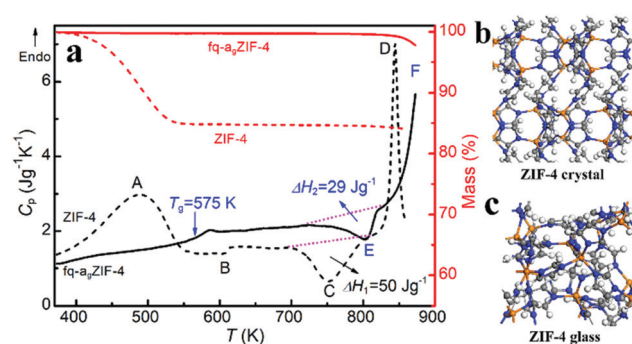


Fig. 1 (a) C_p measurements (black) and thermogravimetric analysis (red) of as-synthesized crystalline ZIF-4 (dashed line) and $a_g\text{ZIF-4}$ (solid line), at a heating rate of 10 K min^{-1} . A: desolvation; B: amorphization; C: recrystallization to ZIF-zni; D: melting; F: decomposition. T_g : glass transition temperature; ΔH_1 : enthalpy released during crystallization of ZIF-zni; ΔH_2 : enthalpy released during the exothermal peak E. (b) Unit cell of ZIF-4 crystal and (c) atomic configuration of the melt-quenched $a_g\text{ZIF-4}$ from ref. 10. Zn – orange, N – blue, C – grey, H – white.

^a State Key Laboratory of Silicate Materials for Architectures, Wuhan University of Technology, Wuhan 430070, China

^b Department of Chemistry and Bioscience, Aalborg University, DK-9220 Aalborg, Denmark

^c Department of Materials Science and Metallurgy, University of Cambridge, Cambridge, CB3 0FS, UK

^d Diamond Light Source Ltd, Diamond House, Harwell Science and Innovation Campus, Didcot OX11 0DE, UK

^e X-ray Science Division, Advanced Photon Source, Argonne National Laboratory, 9700 South Cass Avenue, Argonne, Illinois 60439, USA

^f ISIS Facility, Rutherford Appleton Laboratory, Harwell Campus, Didcot, Oxon OX11 0QX, UK

† Electronic supplementary information (ESI) available. See DOI: 10.1039/c8cc09574d

quenched) for clarity. Reheating fq-a_gZIF-4 (under argon) in the DSC, revealed a glass transition in the region of 565–595 K with the glass transition temperature (T_g) of 575 K (black solid curve in Fig. 1). Curiously, after the glass transition, a broad exothermic peak (marked as E) occurs at ca. 725–820 K. The enthalpy released during this process is 29 J g⁻¹, lower than that of the formation of the crystal ZIF-zni (50 J g⁻¹). Decomposition of the liquid of ZIF-4 glass is then evident at ca. 840 K (point F), which is 30 K lower than the decomposition temperature of the liquid of ZIF-zni, without quenching back to room temperature.⁹

In poor inorganic glass formers, crystallization above the glass transition is common, which causes a narrow and sharp exothermic peak, due to energy release during fast nucleation and crystal growth.^{18,19} To determine whether this occurs here, isothermal heat-treatments were performed on fq-a_gZIF-4, at varying treatment temperatures (T_h), for times (t_h) of 5 and 30 minutes, in the region of the exothermic peak E. PXRD measurements of the resultant material show no sharp Bragg peaks, implying that long-range ordering (LRO) does not occur, i.e., the samples did not recrystallize (Fig. 2a). This behavior is in contrast with many other glass systems where an exothermic response occurred during heat-treatment is representing LRO.

Even prolonged heating of fq-a_gZIF-4 at $T_h = 793$ K for 420 min, did not result in sharp Bragg diffraction (Fig. 2b). This temperature was chosen due to its location at the top of exothermic peak E (Fig. 2a inset). The absence of Bragg diffraction confirms that peak E is not associated with a crystallization process, i.e., LRO, but instead must be attributed to a lowering of enthalpy of the system, and hence, causes the exothermic response, i.e., the release of 29 J g⁻¹ energy.

Samples of fq-a_gZIF-4 were also heat-treated for 5 minutes at temperatures ranging from 748 K to 823 K, before cooling to room temperature (Fig. S1, ESI†). DSC experiments show T_g to be largely unaffected, i.e., both long-range disorder and the glass network connectivity remain unchanged. Heat-treatment at 823 K however resulted in disappearance of the glass transition peak (Fig. S2, ESI†). A sample of fq-a_gZIF-4 was heat-treated at 793 K for 420 min, and the product is hereby referred to as ht-fq-a_gZIF-4 (ht – heat-treated), for clarity. DSC experiments confirmed that the exothermic peak E is present in both fq-a_gZIF-4 and ht-fq-a_gZIF-4 (Fig. S3, ESI†). SEM images show little difference between the two samples, though optical photographs show a distinct darkening in colour after heat-treatment (Fig. S4, ESI†). ¹³C liquid NMR spectroscopy measurements were carried out (Fig. S5 and S6, ESI†) and, as expected, the two ¹³C signals for the glass remain unchanged with increasing T_h , indicating that the local chemical environments of C-1 and C-2 on the imidazolate ring are unaltered during heat-treatment. Pycnometric density measurements demonstrated an increase in density during melt-quenching and heat-treatment. Densities of ZIF-4 crystal, fq-a_gZIF-4 and ht-fq-a_gZIF-4 were recorded as 1.25, 1.67 and 1.76 g cm⁻³, respectively.

Fourier transform infrared (FTIR) spectra using the KBr disc technique were obtained. The full spectra of mid-IR region for the samples of ZIF-4, fq-a_gZIF-4 and ht-fq-a_gZIF-4 are shown in Fig. S7, ESI†. The peaks located at 1681–1475 cm⁻¹ are characteristic of C=C, C=N and imidazolate ring stretching.^{20,21} Both the decreased absorption of the peak near 1680 cm⁻¹ and the increased absorption of the associated weak peak near 1600 cm⁻¹ indicate possible distortion of the imidazolate rings in the ZIF-4 glass upon melt-quenching and heat-treatment. This is further confirmed by the noticeable change of the C-H bending peak near 1387 cm⁻¹. The peak at around 530 cm⁻¹ is assigned to imidazolate ring out-of-plane bending.^{21,22}

To probe any structural differences induced by heat-treatment, room temperature X-ray total scattering measurements were performed on fq-a_gZIF-4 and ht-fq-a_gZIF-4, and compared to previous data on a sample of ZIF-4 glass formed by natural cooling from 853 K, referred to as a_gZIF-4 (Fig. 3).⁸ The absence of Bragg diffraction in the structure factor $S(Q)$ of all samples confirms their amorphous nature and long-range disorder (Fig. 3a), while those for a_gZIF-4 and fq-a_gZIF-4 are near identical. The first sharp diffraction peak (FSDP) for ht-fq-a_gZIF-4 appears to shift slightly to higher Q , which is in accordance with the higher density of this heat-treated sample. Pair distribution functions (PDFs) data were produced by a Fourier transform of these data. The short-range order (SRO) of the samples, i.e. correlations below 6 Å indicating local intra-imidazolate bonds and four local Zn–Im coordinating

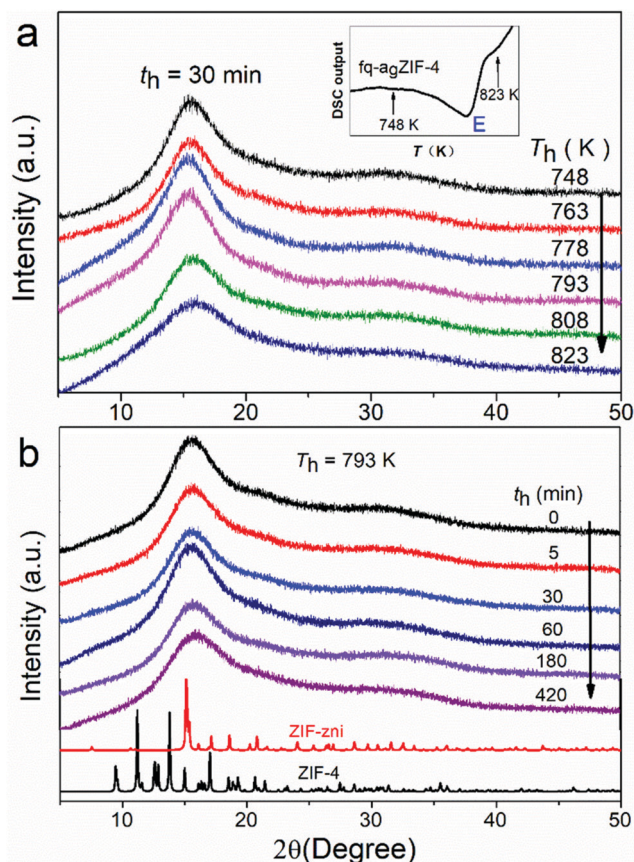


Fig. 2 (a) Powder X-ray diffraction (PXRD) patterns of fq-a_gZIF-4, heat-treated at different temperatures for 30 min. Inset: DSC curve of fq-a_gZIF-4, showing the range of T_h . (b) PXRD patterns of ZIF-4, ZIF-zni, and fq-a_gZIF-4 heat-treated at $T_h = 793$ K for various durations from 0 to 420 min. t_h : heat-treatment duration; T_h : heat-treatment temperature.

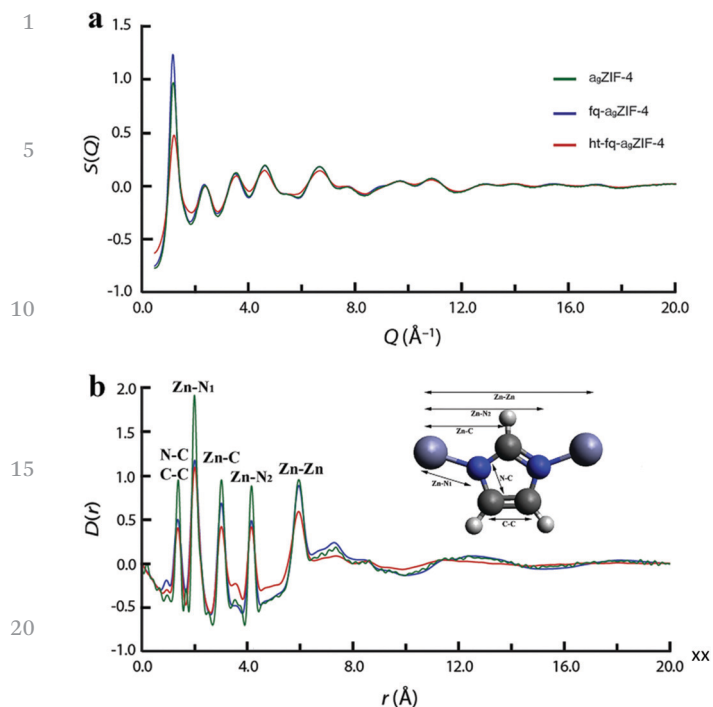


Fig. 3 (a) X-ray total scattering data $S(Q)$ and (b) corresponding X-ray pair distribution functions $D(r)$.

bonds forming a tetrahedron are consistent with those witnessed for glass ZIFs previously.²³ Positions of the peaks belonging to the C-C/C-N, Zn-N, Zn-C, Zn-N and Zn-Zn distances at *ca.* 1.33, 2, 3, 4 and 6 Å are largely unchanged between samples. Specifically, correlations between 6 Å and 8 Å for ht-fq-aqZIF-4 are less distinct upon heat-treatment above T_g . The feature at 7.5 Å, which has previously been ascribed to a M-L-M-L interaction (*i.e.* between Zn and a nitrogen atom of the 2nd nearest imidazolate in this sample),²⁴ is less pronounced. The weaker degree of atomic pair correlations in this region is perhaps associated with structural relaxation (and the associated densification) upon heat-treatment.

To provide a firm structural origin for the exothermic peak E in the DSC scans, high temperature X-ray total scattering measurements, collected on a sample of aqZIF-4 at the APS synchrotron and published previously, were reanalysed.⁸ These data were collected on heating aqZIF-4 at the Advanced Photon Source, US. Temperature intervals were roughly 100 K, from 298 to 778 K (Fig. S8 left, ESI†), and showed little change in the FSDP. However, those obtained in 6 K steps from 778 K to 862 K (Fig. S8 right, ESI†) demonstrated marked changes. A Pseudo-Voigt peak fit was applied to model the position, intensity and width of the FSDP as a function of temperature (Fig. 4). A sharp change at approximately 770 K (*i.e.* close to the onset of the exothermic peak E in Fig. 1a) was seen in all parameters reflecting structural changes in the glass at this temperature (Fig. 4 and Fig S9, ESI†). The increase in position and decrease in intensity qualitatively indicate a densification of the structure.

Hence, holding the as-quenched ZIF-4 glass at 793 K (1.38 T_g) for 420 min can lead to structural densification, towards a lower energy state (*i.e.*, 29 J g⁻¹ lower). The energy released by

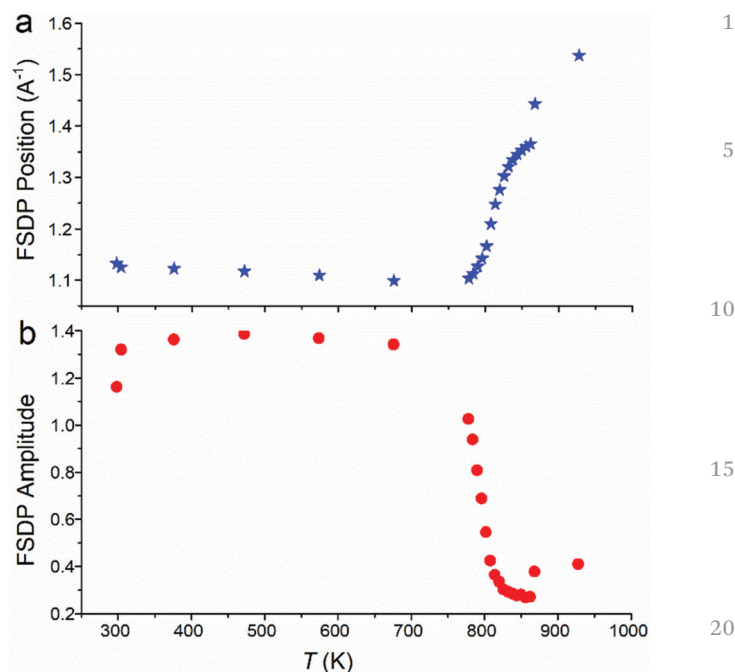


Fig. 4 Variable temperature synchrotron X-ray total scattering data $S(Q)$ showing changes in the (a) position and (b) amplitude of the first sharp diffraction peak (FSDP) with temperature. The two highest temperature points were collected during sample decomposition and above 900 K the pattern mostly consisted of that of the silica capillary.

this process is 3/5 of the energy released by LRO, *i.e.*, crystallization (Peak C in Fig. 1a). This type of relaxation has not been observed in inorganic network glasses. The degree of relaxation is driven by two structural factors of the ZIF-4 glass. First, the size of Zn[Im]₄ tetrahedron is much larger than that of SiO₄ tetrahedron since the Zn-Zn distance (5.9 Å) is much longer than the Si-Si distance (3.1 Å). Second, the coordinating bond between Zn and Im is significantly weaker than the Si-O bonds in oxide glasses. These two factors make the Zn(Im)₄ tetrahedron more ‘floppy’, and hence more distorted after melt-quenching, and therefore pose a higher thermodynamic driving force for relaxation.

Piecing the results together yields a complex picture of structural evolution in aqZIF-4. The absence of crystallization in the glass, even after heat-treatment at high T_h for a long duration, is encouraging for the development of future applications.

YY designed the project. JZ, TDB and YY wrote the manuscript with inputs from other co-authors. All samples were prepared by JZ. DSC, XRD, SEM, L-NMR and FT-IR experiments were performed by JZ and HL, analysed by JZ, YY, HT and HL. Ambient temperature PDF data was collected by LL, CWA, TDB, DAK and PAC. Analysis was performed by LL and DAK. Variable temperature PDF data was collected by TDB, DAK, KAB and KWC, and analysed by LL and DAK.

We thank NSFC (No. 51772223) and Corning Incorporated for the financial support. The authors also thank Malwina Stepniewska, Chao Zhou and Mo Xiong for useful discussions. TDB thanks the Royal Society for a University Research Fellowship (UF150021), LL thanks the EPSRC for a department

allocated studentship, CWA thanks the Royal Society for a studentship under project RG160498. We acknowledge provision of synchrotron access to Beamline I15-1 at the Diamond Light Source (EE171151). This research used resources of the Advanced Photon Source (Beamline 11-ID-B, GUP44665), a U.S. Department of Energy (DOE) Office of Science User Facility operated for the DOE Office of Science by Argonne National Laboratory under Contract No. DE-AC02-06CH11357.

Conflicts of interest

There are no conflicts to declare.

References

- 1 H. Furukawa, K. E. Cordova, M. O'Keeffe and O. M. Yaghi, *Science*, 2013, **341**, 1230444.
- 2 H. Furukawa, N. Ko, Y. B. Go, N. Aratani, S. B. Choi, E. Choi, A. O. Yazaydin, R. Q. Snurr, M. O'Keeffe, J. Kim and O. M. Yaghi, *Science*, 2010, **329**, 424–428.
- 3 L. B. du Bourg, A. U. Ortiz, A. Boutin and F.-X. Coudert, *APL Mater.*, 2014, **2**, 124110.
- 4 K. S. Park, Z. Ni, A. P. Côté, J. Y. Choi, R. Huang, F. J. Uribe-Romo, H. K. Chae, M. O'Keeffe and O. M. Yaghi, *Proc. Natl. Acad. Sci. U. S. A.*, 2006, **103**, 10186–10191.
- 5 Y. Q. Tian, Y. M. Zhao, Z. X. Chen, G. N. Zhang, L. H. Weng and D. Y. Zhao, *Chem. – Eur. J.*, 2007, **13**, 4146–4154.
- 6 T. D. Bennett, D. A. Keen, J. C. Tan, E. R. Barney, A. L. Goodwin and A. K. Cheetham, *Angew. Chem., Int. Ed. Engl.*, 2011, **50**, 3067–3071.
- 7 K. W. Chapman, G. J. Halder and P. J. Chupas, *J. Am. Chem. Soc.*, 2009, **131**, 17546–17547.
- 8 R. Gaillac, P. Pullumbi, K. A. Beyer, K. W. Chapman, D. A. Keen, T. D. Bennett and F. X. Coudert, *Nat. Mater.*, 2017, **16**, 1149–1154.
- 9 T. D. Bennett, J. C. Tan, Y. Z. Yue, E. Baxter, C. Ducati, N. J. Terrill, H. H. Yeung, Z. Zhou, W. Chen, S. Henke, A. K. Cheetham and G. N. Greaves, *Nat. Commun.*, 2015, **6**, 8079.
- 10 P. Adhikari, M. Xiong, N. Li, X. Zhao, P. Rulis and W.-Y. Ching, *J. Phys. Chem. C*, 2016, **120**, 15362–15368.
- 11 D. Xu, Y. Liu, Y. Tian and L.-M. Wang, *J. Chem. Phys.*, 2017, **146**, 121101.
- 12 T. D. Bennett, Y. Yue, P. Li, A. Qiao, H. Tao, N. G. Greaves, T. Richards, G. I. Lampronti, S. A. Redfern and F. Blanc, *J. Am. Chem. Soc.*, 2016, **138**, 3484–3492.
- 13 H. Shintani and H. Tanaka, *Nat. Phys.*, 2006, **2**, 200–206.
- 14 T. Kawasaki, T. Araki and H. Tanaka, *Phys. Rev. Lett.*, 2007, **99**, 215701.
- 15 T. Besara, P. Jain, N. S. Dalal, P. L. Kuhns, A. P. Reyes, H. W. Kroto and A. K. Cheetham, *Proc. Natl. Acad. Sci. U. S. A.*, 2011, **108**, 6828–6832.
- 16 A. Qiao, T. D. Bennett, H. Tao, A. Krajnc, G. Mali, C. M. Doherty, A. W. Thornton, J. C. Mauro, G. N. Greaves and Y. Z. Yue, *Sci. Adv.*, 2018, **4**, eaao6827.
- 17 A. W. Thornton, K. E. Jelfs, K. Konstas, C. M. Doherty, A. J. Hill, A. K. Cheetham and T. D. Bennett, *Chem. Commun.*, 2016, **52**, 3750–3753.
- 18 N. Karpukhina, R. G. Hill and R. V. Law, *Chem. Soc. Rev.*, 2014, **43**, 2174–2186.
- 19 S. Pogatscher, P. J. Uggowitzer and J. F. Löffler, *Appl. Phys. Lett.*, 2014, **104**, 251908.
- 20 M. R. Ryder, T. D. Bennett, C. S. Kelley, M. D. Frogley, G. Cinque and J. C. Tan, *Chem. Commun.*, 2017, **53**, 7041–7044.
- 21 Y. Hu, H. Kazemian, S. Rohani, Y. Huang and Y. Song, *Chem. Commun.*, 2011, **47**, 12694–12696.
- 22 M. R. Ryder, B. Civalleri, T. D. Bennett, S. Henke, S. Rudic, G. Cinque, F. Fernandez-Alonso and J. C. Tan, *Phys. Rev. Lett.*, 2014, **113**, 215502.
- 23 T. D. Bennett and A. K. Cheetham, *Acc. Chem. Res.*, 2014, **47**, 1555–1562.
- 24 C. Zhou, L. Longley, A. Krajnc, G. Smales, A. Qiao, I. Erucar, C. Doherty, A. Thornton, A. J. Hill, C. Ashling, O. Qazvini, S. J. Lee, P. Chater, N. Terrill, A. J. Smith, Y. Z. Yue, G. Mali, D. A. Keen, S. Telfer and T. Bennett, *Nat. Commun.*, 2018, **9**, 5042.